

# The effects of mineralogical and petrographical features of the Lake District rocks (Isparta, Turkey) on the quality of artificial marbles

**ALI BILGIN** ▪ Sırnak University, Department of Mining, Batman, Turkey

**GURKAN YUCETURK** ▪ Suleyman Demirel University, Department of Geology, Isparta, Turkey

**SONMEZ ARSLAN** ▪ Batman University, Department of Chemistry, Batman, Turkey

**NURSEV BILGIN** ▪ Middle East Technical University, Department of Materials Science, Ankara, Turkey

**SULEYMAN POLAT** ▪ Batman University, Department of Geology, Batman, Turkey

Érkezett: 2013. 03. 27. ▪ Received: 27. 03. 2013. ▪ <http://dx.doi.org/10.14382/epitoanyag-jsbcm.2013.5>

## Abstract

Large quantities of marble blocks are produced from many new marble quarries which were opened around Isparta (Turkey) and its surrounding region. The opened quarries are also affected negatively by weathering as a result of karstification. Therefore, block efficiency of the quarries is low which results in a lot of waste materials that can be used in cultured marble production. The production of artificial marble from marble waste materials around Isparta is the main purpose of the study. The cultured marble is an attractive, healthy and homogenous building material. It has a wide application in the building construction sector. Artificial marble which is composed of mineral dusts and polyesters has high mechanical strength and they are durable to various chemical and high temperature environmental conditions. Based on physico-mechanical properties, cultured marbles are accepted by Turkish Standards (TS). The materials used for the production of qualified cultured marble are directly related to the hardness of the minerals used as filler in the polyester resin. Physico-mechanical properties of cultured marble depend on the physical properties of the filler minerals. The compressive strength of the cultured marble material is controlled by the physical properties of the filler minerals, therefore, the hardness of the cultured marble is determined by the hardness of the filler mineral. The following analyses were carried out: wet unit volume analysis, dry unit volume analysis, compressive strength of the materials, capillary water absorption analysis, analysis of ultrasound velocity (P-wave) and the marble wastes bulk chemical analyses were investigated and the results of the data were evaluated and discussed. In addition, natural and artificial marbles were compared with respect to physico-mechanical properties.

Keywords: artificial marble, polyester resin, marble quarry, compressive strength.

## 1. Introduction

Wastes of rocks similarly to all kinds of construction materials and industrial raw materials used in our daily life may adversely influence the environment. Evaluation of the waste materials and turning into economic value has important issue at present time. Large quantities of marble blocks are produced from many new marble quarries which were opened around Isparta-Burdur (Turkey) which has rich marble fields in its surrounding region (Fig. 1). The opened quarries are also negatively affected by weathering as a result of karstification. Therefore block efficiency of the quarries is low and they produce a lot of waste materials [1]. There are many ways to evaluate these produced wastes [2]. Granulated artificial marble dusts in micron size in mills mixing and molding in different ratios with resins have been evaluated as cultured marble artificial construction material [3]. One of the evaluation methods of waste marble is using them in production of cultured marble. The production of artificial marble from natural marble waste materials around Isparta-Burdur area is the main purpose of this research.

## Ali BILGIN

Received his BSc degree in 1972, Middle East Technical University Faculty of Engineering Department of Geological Engineering, Ankara, Turkey. Received his PhD degree in 1978, Ataturk University, Faculty of Natural Sciences, Department of Geology, Erzurum, Turkey. He is currently full Professor at Sırnak University Faculty of Engineering Department of Mining Engineering.

## Gurkan YÜCETÜRK

Received his MSc degree from the Süleyman Demirel University, Turkey. Received his PhD degree from the Süleyman Demirel University, Turkey. He is currently project manager at Ekinçiler Co, Turkey.

## Sonmez ARSLAN

Received his PhD degree in 2008, Istanbul Technical University, Department of Chemistry, Istanbul, Turkey. He is currently Assistant Professor at Batman University, Faculty of Arts and Science, Department Of Chemistry, Batman, Turkey.

## Nursev BILGIN

Received his BSc and MSc degrees from Yildiz Technical University Faculty, Istanbul, Turkey. Received his PhD degree in 2011, Middle East Technical University, Ankara, Turkey. He is currently Research Assistant at Middle East Technical University, Ankara, Turkey. Research Interests: Solar cells, DSSCs, TiO<sub>2</sub>, clay minerals.

## Suleyman POLAT

Received his MSc degree in 2012, Suleyman Demirel Middle University Faculty of Engineering, Department of Geological Engineering, Isparta, Turkey. He is currently Research Assistant at Batman University, Faculty of Engineering and Architecture Geological Engineering Department, Batman, Turkey.



Fig. 1. Location map of the study area.

1. ábra A vizsgálati helyszínek térképvázlata

Marble blocks produced at marble quarries leave huge quantities of marble wastes which results waste marble hills with visual pollution (Fig. 2) [2]. Wollastonite, quartz and other silicate minerals are significant materials used for artificial marble production as well, additional to marble waste. Calcite and dolomite are considered in carbonate group minerals and the effect of the ratios of the resins and additive materials on cultured marble materials is still under discussion [4].



Fig. 2. Waste marble hills in Isparta-Burdur area which cause visual pollution  
2. ábra Vizuális szennyezést okozó hulladék márvány dombok az Isparta-Burdur területen

## 2. Materials and methods

### 2.1. Samples location

There are many marble deposits around Isparta and Burdur area. We have collected 12 samples from waste marbles; locations are indicated in Fig. 3.

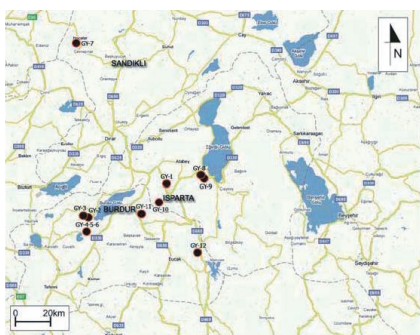


Fig. 3. Waste marble sample locations around Burdur and Isparta.  
3. ábra Hulladék márvány mintavételi helyek Burdur és Isparta környékén

### 2.2. Used materials for artificial marble production

Artificial marbles have been produced from calcite, quartz, feldspar and wollastonite that can be found in waste marble dusts mixing with polymer resin materials. Resins are used as binder, calcite, dolomite, quartz and wollastonite minerals are used as aggregate/filler for cultured marbles and waste glass is also used for artificial marble production as additive material [5].

## 3. Results and discussions

### 3.1. Texture of artificial marbles

Polarization microscopy analysis was made first to study the texture of artificial marble raw materials. For the inspection, sections of 30 µm thickness were prepared to identify the mineral composition of the waste marble samples. Some of the samples could not be determined by means of polarization microscopy due to the grain size smaller than 2 µm. Those samples were investigated by differential thermal analysis (DTA) and scanning electron microscope (SEM). The texture of sedimentary marbles was found to be micritic texture; the andesites have porphyritic texture which has phenocrysts in glass. The scanning electron microscope investigation of the texture of the produced cultured marble is shown in Fig. 4. It has clastic texture where the grains are marble surrounded

by the resin. The resin is amorphous material, therefore, the light cannot be transmitted through it (appears in dark colour in Fig. 4). Calcite grains are transparent and permit the light transmitting through them (appear in light colour in Fig. 4).

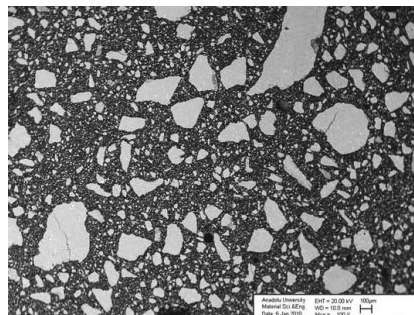


Fig. 4. Clastic texture of artificial marble through secondary electron SEM images of calcite grains (Sample-1, Söbudağ Limestone, North of Isparta).  
4. ábra Mesterséges márvány klasztikus szövete, kalcit szemcsék pászttázó elektronmikroszkópos felvételén (1. sz. minta, Söbudağ mészkő, Észak-Isparta).

### 3.2. Characterization of the artificial marble

For the characterization of the calcite and dolomite minerals, SEM and DTA analyses were carried out (Fig. 4 and 5). Sedimentary marbles have micritic texture containing micritic types of calcite and dolomite minerals depending on their composition. They could not be determined by polarization microscopy, therefore, we applied differential thermal analysis (DTA) to study the mineralogical composition, by preparing powder sample. The sample was heated up to 1200°C and exothermic and endothermic peaks were noted at certain points. Endothermic peaks between 800 and 900°C belong to calcite and dolomite. The obtained results were evaluated by ASTM cards which confirmed the composition of minerals being a mixture of dolomite and calcite.

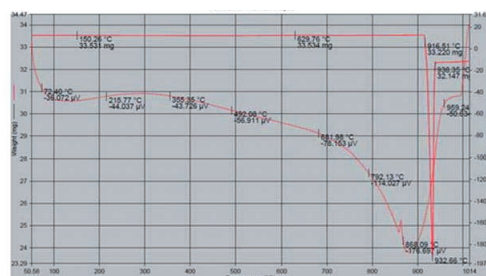


Fig. 5. DTA diagram of carbonate mineral (Söbudağ, North of Isparta).  
5. ábra Karbonátos ásvány DTA diagramja (Söbudağ, Észak-Isparta).

### 3.3. Properties of the artificial marbles

Chemical composition of marble is changing with respect to the type of marbles. Igneous marbles have high SiO<sub>2</sub> but sedimentary types of marbles have higher Ca-Mg-CO<sub>3</sub> (Table 1).

Mineralogy of the minerals used as an additive in artificial marbles controls the quality of the cultured marbles. Therefore, mineralogy of the used additive materials has to be investigated in detail with respect to physical properties. These are especially hardness, grain size and morphology and thermal properties. Raw waste marble samples contain calcite, dolomite, quartz, mica, feldspar, serpentine group minerals and wollastonite.

Sample	Limestone								Trachy-andesite		Travertine	
	GY1	GY2	GY3	GY4	GY5	GY6	GY7	GY8	GY9	GY10	GY11	GY12
Number	GY1	GY2	GY3	GY4	GY5	GY6	GY7	GY8	GY9	GY10	GY11	GY12
SiO <sub>2</sub>	0.11	0.09	0.02	0.16	0.07	0.01	0.1	0.02	0.07	57.6	0.21	0.03
TiO <sub>2</sub>	0	0	0	0	0	0	0	0	0	0.43	0.00	0.00
Al <sub>2</sub> O <sub>3</sub>	0.01	0.01	0.02	0.01	0.01	0.02	0.04	0.01	0.04	17.1	0.02	0.01
Fe <sub>2</sub> O <sub>3</sub>	0.06	0.04	0.03	0.05	0.04	0.02	0.09	0.02	0.07	4.14	0.20	0.05
MnO	0.01	0.01	0.01	0.01	0.01	0.01	0.02	0.01	0.01	0.13	0.04	0.01
MgO	0.61	0.56	0.74	0.54	18.4	0.43	0.5	0.44	0.47	1.33	0.40	0.47
CaO	53.3	54.1	53.8	54.8	33.8	54.7	53.5	54.8	54.5	4.89	53.70	54.7
Na <sub>2</sub> O	0.52	0.5	0.49	0.49	0.51	0.47	0.53	0.47	0.5	5.0	0.46	0.50
K <sub>2</sub> O	0.58	0.56	0.56	0.57	0.55	0.53	0.6	0.52	0.57	4.86	0.57	0.58
P <sub>2</sub> O <sub>5</sub>	0.02	0.02	0.02	0.03	0.04	0.01	0.03	0.02	0.02	0.24	0.02	0.01
Ignition lost	43.7	43.1	43.4	43.2	46.5	43.2	43.2	43.2	42.8	3.21	43.90	43.30
Total	98.9	98.9	99.2	99.8	99.8	99.5	98.6	99.6	99.2	98.9	99.60	99.70

Table 1. Chemical composition of natural marbles which used for artificial marble production.  
1. táblázat A mesterséges márvány készítésére használt márványok kémiai összetétele

Calcite and dolomite belong to carbonate group minerals. Their hardness values are 3 and 4 with respect to Mohs hardness scale, respectively. When artificial marble is produced by using carbonate minerals its compressive strength is lower. As hardness of the minerals increases, its compressive strength increases too. On the other hand, trachy-andesites containing feldspar and quartz which belong to silicate group minerals give higher compressive strength and have higher hardness value between 6 and 7 with respect to Mohs hardness scale.

In artificial marble production, grain size morphology is important if high temperature resistant material is intended to be produced. Wollastonite has fiber grain morphology and is resistant to high temperature [6]. It has a unique property with fibrous morphology and also refractory feature (Fig. 6). The materials containing wollastonite can be used effectively in high temperature conditions. It has also high corrosion resistance. When it is used as an additive material in artificial marbles it may result higher compressive strength, higher durability, refractory feature and corrosion resistance.



Fig. 6. Fibrous structure of wollastonite (<http://www.google.com.tr/imgres>)  
6. ábra Wollastonit szálas szerkezete (<http://www.google.com.tr/imgres>)

Sample Number	Dry Weight (g)	After 24 Hours (g)	After 48 Hours (g)	After 72 Hours (g)	Water Absorption (%)
GY-1	250.70	250.70	250.70	250.73	0.03
GY-2	250.70	250.70	250.80	250.80	0.04
GY-3	250.57	250.57	250.60	250.60	0.03
GY-4	249.53	249.53	249.57	249.57	0.01
GY-5	253.70	253.70	253.77	253.77	0.03
GY-6	233.67	233.67	233.83	233.83	0.07
GY-7	246.00	246.00	246.00	246.00	0.00
GY-8	247.83	247.83	247.97	247.97	0.05
GY-9	243.43	243.43	243.43	243.43	0.00
GY-10	245.30	245.40	245.50	245.50	0.08
GY-11	250.70	250.73	250.83	250.83	0.05
GY-12	248.93	249.00	249.10	249.10	0.07

Table 2. Water absorption of cultured marble samples according to Turkish Standards (TS)

2. táblázat A mesterséges márvány minták vízfelvétele a Török Szabványok (TS) szerint vizsgálva

Grain morphology also controls the quality of artificial marble. Wollastonite and chrysotile have fibrous grain morphology. They contribute to higher strength of the materials similarly to steel rebar in concrete. Although wollastonite and chrysotile are useful for the best quality of the artificial marble but chrysotile is considered to be carcinogenic so it is not preferred for the production of the cultured marble [7,8].

Weights of wet unit volume (WWUV) of artificial marble cubic samples were evaluated (Table 3). Natural marbles have some porosity which adversely affects the quality of the marble. When natural marbles have porosity of percolated capillaries, water may be absorbed into the material and cause the weathering physically and chemically. Therefore, porosity



of the marbles should be close to zero (Table 3). The water absorption was found to be low (values vary between 0.00 % and 0.08 %) for the cultured marble samples tested (Table 3). It means that the products are compact and have negligible amount of porosity. The low porosity can make the material durable against water and air.

Sample Number	WDUV (kg/m <sup>3</sup> )	WWUV (kg/m <sup>3</sup> )	Porosity (n) %
GY-1	1993.12	2004.01	5.32
GY-2	2015.24	2021.15	4.12
GY-3	2012.89	2014.83	5.36
GY-4	1994.60	1997.34	6.68
GY-5	2044.84	2060.28	5.08
GY-6	1903.50	1888.97	3.88
GY-7	1976.40	1972.66	3.88
GY-8	2010.73	2011.22	2.40
GY-9	1989.50	1996.51	6.80
GY-10	1908.49	1908.40	10.00
GY-11	2026.56	2024.98	10.00
GY-12	1971.53	1981.90	11.72

Table 3. Weights of dry unit volume (WDUV), weights of wet unit volume (WWUV) and apparent porosity of artificial marble cubic samples

3. táblázat A mesterséges márvány próbakockák mért nedves testsűrűsége, száraz testsűrűsége és látszólagos porozitása

Table 4 summarizes the compressive strength, the ultrasound pulse velocity and the rebound index values corresponding to the artificial marbles produced.

Sample Number	Compressive strength N/mm <sup>2</sup>	Ultrasound pulse velocity Vp (m/s)	Rebound index
GY-1	106.13	3555	34
GY-2	98.69	3509	34
GY-3	91.21	3478	34
GY-4	72.17	3503	34
GY-5	64.93	3406	34
GY-6	83.51	3271	34
GY-7	82.29	3440	34
GY-8	97.11	3461	34
GY-9	71.86	3426	34
GY-10	61.16	3399	34
GY-11	76.32	3516	34
GY-12	68.88	3601	34

Table 4. Compressive strength, ultrasound pulse velocity and rebound index of artificial marble cubic samples

4. táblázat A mesterséges márvány próbakockákon mért nyomószilárdság, ultrahang terjedési sebesség és visszapattanási érték

Construction materials should have some physico-mechanical values required in building industry. Required values for natural building stones are summarized in Table 5

[9]. When we compared cultured marble with natural building stone, our results were found above the required values. Therefore, our produced artificial marbles can be safely used in the building industry as a constructional material.

TS	Standard Name	Used Place	Uniaxial compressive strength N/mm <sup>2</sup>
11137	Limestone	Floor covering	50 N/mm <sup>2</sup>
		Wall covering	30 N/mm <sup>2</sup>
10835	Andesite	Floor covering	100 N/mm <sup>2</sup>
		Wall covering	60 N/mm <sup>2</sup>
11135	Trachyte	Floor covering	80 N/mm <sup>2</sup>
		Wall covering	50 N/mm <sup>2</sup>
10449	Marble (calcium carbonate)	Floor covering	50 N/mm <sup>2</sup>
		Wall covering	30 N/mm <sup>2</sup>
11143	Travertine	Floor covering	48 N/mm <sup>2</sup>
		Wall covering	30 N/mm <sup>2</sup>

Table 5. Minimum values required by the uniaxial compressive strength (TS EN 1926) 5. táblázat Egytengelyű nyomószilárdság előírt legkisebb értékei (TS EN 1926)

#### 4. Conclusions

Large quantities of marble blocks are produced from many new marble quarries which were opened around Isparta (Turkey) and its surrounding region. Block efficiency of the quarries is low which results in a lot of waste materials that can be used in cultured marble production. The cultured marble is an attractive, healthy and homogenous building material. It has a wide application in the building sector. Artificial marble which is composed of mineral waste materials and polyester resins has high compressive strength, durable to various chemical and high temperature environmental conditions. Based on physico-mechanical properties, cultured marbles are accepted by the Turkish Standards (TS). Physico-mechanical properties of cultured marble depend on the physical properties of the filler minerals. The following analyses; wet unit volume analysis, dry unit volume analysis, compressive strength of the materials, capillary water absorption analysis, ultrasound pulse velocity analysis and the marble wastes bulk chemical analyses were carried out and the results were evaluated and discussed with respect to the physico-mechanical properties.

Tensile Strength	45	MPa	ISO 527
Breaking Elongation	1.3	%	ISO 527
Tensile Modulus	3800	MPa	ISO 527
Bending Strength	70	MPa	ISO 178
Bending Modulus	3900	MPa	ISO 178
HDT	95	°C	ISO 75A
Hardness	45	Barcol	934-1

Table 6. Various physico-mechanical values of resins 6. táblázat Műgyanták különféle fizikai/mechanikai jellemzői

Construction materials should have important physico-mechanical values required in building industry. When we compared our artificial marbles with natural building stones, our results all met the requirements. Therefore, our artificial marbles can be safely used in the building industry as a construction material. The artificial marbles are resistant to acids, alkalis and they are cheap and durable so there is a huge potential in them to be used in harsh environments. Artificial marble has anti-bacterial property so it has been widely used in baths, hospitals, hotels, restaurants. Artificial marble production has positive effect on environmental concerns by elimination of marble wastes as well.

## 5. Acknowledgments

Authors are thankful to Prof. Dr. Lütfullah Gündüz in Pumice Applied Research Center Manager of Suleyman Demirel University for the analyses of all of the physico-mechanical properties of the artificial marbles.

### References

- [1] Bilgin, A. – Özkahraman, T.: *Marble potential of Isparta and some related problems*. International Symposium on Engineering and Architectural Sciences, Balkan Caucasus and Turkic Republics. I, 22-24 October, Isparta, Turkey, pp. 231-237. 2009
- [2] Bilgin, N. – Yeprem, H. A. – Arslan, S. – Bilgin, A. – Günay, E. – Marşoğlu, M.: *Use of Waste Marble Powder in Brick Industry*. Construction and Building Materials, Issue 4, Vol. 29, pp. 449-457. 2012
- [3] Hussin, K. – Baharin, S. – Ghazali, Ç. M. R. – Idris, M. S. – Salleh, M. N. I. K. N.: *The Development Of Artificial Marble From Dolomite (Batu Reput) In Perlis*. KUKUM Engineering Research Seminar, 2006
- [4] Aruniit, A. – Kers, J. – Tall, K.: *Influence of filler proportion on mechanical and physical properties of particulate composite*. Agronomy Research Biosystem Engineering Special Issue 1, pp. 23-29. 2011
- [5] Lee, M. Y.: *Anti-bacterial self-cleansing stone slab and its manufacturing method*. TW Patent 189048. 2004
- [6] Berry, L. G. – Mason, B. – Dietrich, R. V.: *Mineralogy*. Freeman and Company, San Francisco, p. 459. 1983
- [7] Chen, T. W. – Ding, Y. C. – Chiu, J. P.: *A study of synthetic forsterite refractory materials using waste serpentine cutting*. Minerals Engineering, 15, pp. 271-275. 2002

## FOLYÓIRATSZEMLE

### A. Hellebois, A. Launoy, C. Pierre, M. De Lanève, B. Espion: 100-year-old Hennebique concrete, from composition to performance

Construction and Building Materials (Elsevier) ISSN 0950-0618, Volume 44 (2013) pp. 149-160.

A belga szerzők angol nyelvű cikke egy 1904-ben épült, 2010-ben elbontott vasbeton vasúti híd beton anyagának a vizsgálatait mutatja be. A híd (Viduc Colo-Hugues) Belgiumban, Braine-l'Alleud városában épült Hennebique eredeti szabadalma alapján. A híd eredetileg egy 13-nyílású, 73 m hosszú, 3,80 m széles szerkezet volt, amelyet az 1960-as évektől nem használtak, és a vizsgálatok időpontjában már csak öt nyílása volt meg. A 106 éves szerkezet korához képest jó állapotban volt a vizsgálatok időpontjában annak ellenére, hogy a Hennebique-féle kivitelezési technológia (pl. távtartókat nem használtak a betonacélok elhelyezésekor) következtében már a kivitelezés során kialakultak káros elváltozások (kis betonfedés a pontatlan betonacél elhelyezés miatt; fészkes, rosszul bedolgozott beton stb.). Elvégezték a nyomószilárdság, hasító-húzószilárdság, rugalmassági modulus, testsűrűség, vízfelvétel, karbonátosodási mélység, klorid-ion tartalom, cement tartalom

- [8] Lee, M-Y. – Ko, C-H. – Chang, F-C. – Lo, S-L. – Lin, J-D. – Shan, M-Y. – Lee, J-C.: *Artificial stone slab production using waste glass, stone fragments and vacuum vibratory compaction*. Elsevier, Cement & Concrete Composites, 30, pp. 583-587. 2008
- [9] Yüçeturk, G.: *Yapay mermerde kullanılan kuvar ve kalsit minerallerinin fizikoklasik özellikleri*. Constructional Technology, V.2, 3, pp. 72-80. 2010

### Ref.:

A. Bilgin – G. Yuceturk – S. Arslan – N. Bilgin – S. Polat: *The effects of mineralogical and petrographical features of the Lake District rocks (Isparta, Turkey) on the quality of artificial marbles*. *Építőanyag*, 65. évf. 1. szám (2013), 21–25. p. <http://dx.doi.org/10.14382/epitoanyag-jsbcm.2013.5>

### A Lake District kőzetek (Isparta, Törökország) ásványtani és kőzettani jellegzetességeinek hatása mesterséges márványok minőségére

Törökországban, Isparta város környezetében számos márványbánya nyílt az elmúlt évtizedekben. A helyenként számottevő karsztosodás miatt a kőzettömbök kitermelésének hatékonysága nem optimális, és nagy mennyiségű hulladék márvány töret keletkezik. A hulladék anyag depóniák jelentős vizuális szennyezést eredményeznek. A hulladék márvány alkalmas mesterséges márvány készítésére, poliészter gyantával kombinálva. A mesterséges márvány nagy tartósságú építőanyag, ellenáll agresszív kémiai hatásoknak és esetenként magas hőmérsékletnek is, ezért a Török Szabványok (TS) elfogadják a mesterséges márvány építőanyagként történő alkalmazását. A mesterséges márvány fizikai/mechanikai jellemzői elsősorban a márvány zúzalék és por jellemzőitől függenek, így azok kémiai elemzése kiemelt jelentőségű. A cikk az Isparta közelében elhelyezkedő egyes márványbányákból származó hulladék márvány felhasználásával készített mesterséges márvány minták vizsgálatát mutatja be. Elemzi a vízfelvételi, tömegeloszlási, porozitási, nyomószilárdsági, ultrahang terjedési és felületi keménységi vizsgálatok eredményeit, illetve bemutatja a vizsgálatokhoz kapcsolódó termogravimetriai és pásztázó elektronmikroszkópos vizsgálatok egyes eredményeit. A bemutatott eredmények alátámasztják a megvizsgált mesterséges márványok építőipari alkalmazhatóságát.

Kulcsszavak: mesterséges márvány, poliészter gyanta, márványbánya, nyomószilárdság

vizsgálatát. Az adalékanyag feltárását követően annak szemeloszlási és petrográfiai jellemzőit is meghatározták. Az eredmények szerint a szerkezeti elemek cement tartalma ( $c$ ,  $\text{kg/m}^3$ ) és nyomószilárdsága ( $f_{cm}$ , MPa) változatos volt: pillérek  $c = 131-144 \text{ kg/m}^3$  és  $f_{cm} = 19,7 \text{ MPa}$ ; gerendák  $c = 247-273 \text{ kg/m}^3$  és  $f_{cm} = 34,6 \text{ MPa}$ ; lemezek  $c = 291-308 \text{ kg/m}^3$  és  $f_{cm} = 54,2 \text{ MPa}$ . A petrográfiai vizsgálatok szerint az adalékanyag egy, a közelben megtalálható, nagy szilárdságú, de erózióra hajlamos, andezit-dácit típusú, porfiros kőzetanyagból készülhetett. A szemeloszlási vizsgálatok szerint az adalékanyag 0,5 mm/2,0 mm frakciója csaknem teljesen hiányzott a keverékből, ezzel szemben a 0,25 mm/0,5 mm frakció a napjainkban megszokottnál nagyobb mennyiségben került a betonba. A karbonátosodás átlagos mélysége 18,6 mm volt a pilléreknél, 18,7 mm volt a gerendáknál és 8,3 mm volt a lemezeknél. A betonacélokat a karbonátosodás mélysége csak kevés helyen érte el. A szerkezeti beton klorid-ion tartalma a kritikus klorid-ion tartalom (0,4 m%/cement) egy tizedét sem érte el, amely a korabeli kalcium-klorid adalékszerből származott. A vizsgálatok bizonyították, hogy a XX. század elején elérhető anyagokkal és technológiákkal is lehetett nagy tartósságú betonszerkezeteket építeni abban az esetben, ha az anyagválasztás, a tervezés és a kivitelezés megfelelő és gondosan ellenőrzött volt.